

Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

**jmr&t**  
Journal of Materials Research and Technology  
[www.jmrt.com.br](http://www.jmrt.com.br)



## Original Article

# Synthesis of FeF<sub>2</sub>/carbon composite nanoparticle by one-pot solid state reaction as cathode material for lithium-ion battery

Mengyun Tang<sup>a</sup>, Zhengfu Zhang<sup>a,\*</sup>, Zi Wang<sup>a</sup>, Jingfeng Liu<sup>a</sup>, Hongge Yan<sup>b</sup>, Jinhui Peng<sup>c</sup>, Lei Xu<sup>c</sup>, Shenghui Guo<sup>c</sup>, Shaohua Ju<sup>c</sup>, Guo Chen<sup>c</sup>

<sup>a</sup> Faculty of Materials Science and Engineering, Kunming University of Science and Technology, 650093 Kunming, China

<sup>b</sup> College of Materials Science and Engineering, Hunan University, Changsha 410082, China

<sup>c</sup> National Local Joint Engineering Laboratory of Engineering Applications of Microwave Energy and Equipment Technology, Kunming 650093, China

## ARTICLE INFO

## Article history:

Received 15 January 2017

Accepted 25 May 2017

Available online 12 August 2017

## Keywords:

Lithium-ion battery

FeF<sub>2</sub>

Nanoparticles

Cathode material

Charge–discharge performance

## ABSTRACT

FeF<sub>2</sub>/carbon composite nanoparticle was prepared by a one-pot thermal reaction using a mixture of ferrous oxalate and PTFE as precursor. FeF<sub>2</sub> was obtained as the main phase according to the XRD patterns of the samples prepared in the present study. Furthermore, the FeF<sub>2</sub> particle has a size of 50–100 nm. Its electrochemical properties were studied in the 4.2–1.3 V region at a current density of 60 mA g<sup>-1</sup>. It exhibited an initial discharge capacity of 503.394 mA h g<sup>-1</sup> and still reserved discharge capacity of about 268.478, 211.34, 193.817 and 183.328 mA h g<sup>-1</sup> at the 2nd, 3rd, 10th, and 20th cycles, respectively.

© 2017 Brazilian Metallurgical, Materials and Mining Association. Published by Elsevier Editora Ltda. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

## 1. Introduction

Lithium-ion batteries (LIBs) are important energy storage devices, and they are required with higher energy density for usage in electric/hybrid vehicle and grid scale storage [1]. As the commercial cathode material LiCoO<sub>2</sub> or LiFePO<sub>4</sub> has a capacity of 150 or 170 mA h g<sup>-1</sup>, the key to improve the energy density of LIBs is looking for electrode materials with higher energy density [2]. Metal fluoride can store more than one lithium per molecule or per molecular unit a multi-electron

conversion reaction, so its theoretical capacity can be very high. Besides, metal fluoride has a high voltage potential brought by high ionicity of M–F bond [3]. Iron fluoride is one of the most potential candidates used as cathode materials due to its high specific capacity, low cost, and low toxicity [4–6]. FeF<sub>2</sub> has a capacity of 571 mA h g<sup>-1</sup> and thermodynamic reduction potential with Li is 2.66 V [7–9]. So it is a good candidate for high energy density LIBs.

FeF<sub>2</sub>/carbon nanoparticles were prepared by a one-pot thermal reaction using a simple procedure based on the thermal decomposition and reaction of a mixture of ferrous oxalate

\* Corresponding author.

E-mail: [zhang-zhengfu@163.com](mailto:zhang-zhengfu@163.com) (Z. Zhang).

<https://doi.org/10.1016/j.jmrt.2017.05.013>

2238-7854/© 2017 Brazilian Metallurgical, Materials and Mining Association. Published by Elsevier Editora Ltda. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

and PTFE. The composite's electrochemical property as cathode electrode is tested.

## 2. Material and methods

### 2.1. Experiment

The ferrous oxalate powder ( $\text{FeC}_2\text{O}_4$ ) and PTFE ( $(\text{C}_2\text{F}_4)_n$ ) powder were utilized as experimental raw materials. First, ferrous oxalate and PTFE were mixed using mortar and pestle. The weight ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}]$  was varied from 10:2.78 to 10:4.17, in which amount of PTFE are larger than that of a stoichiometric ratio. The PTFE is decomposed at low temperature between 400 and 600 °C [10]. Then, the homogeneous mixture was heated in an Ar atmosphere at a rate of 8 °C/min up to 500, 550 and 650 °C. This temperature was kept for 1 h and cooled to room temperature naturally. Finally, the product was collected and then subjected to structure and property characterization.

### 2.2. Characterization

The crystal structure of the product was characterized by X-ray diffraction using Bruker D8 with Cu  $K\alpha$  radiation ( $\lambda = 1.5406 \text{ \AA}$ ). Transmission electron microscopy (TEM) measurements were made on a Hitachi H-8100 electron microscope with an accelerating voltage of 200 kV.

The electrodes were prepared by mixing active materials (80 wt%), acetylene black (10 wt%), and polyvinylidene fluoride (PVDF, 10 wt%) in N-methyl-2-pyrrolidone (NMP). After the above slurries were uniformly spread onto an aluminum foil, the electrodes were dried at 100 °C in vacuum for 24 h. Then electrodes were pressed and cut into disks before transferring into an Argon-filled glove box. Coin cells (CR2025) were assembled using lithium metal as the counter electrode, Celgard 2400 membrane as the separator and  $\text{LiPF}_6$  (1 M) in ethylene carbonate/dimethyl carbonate/ethylmethyl carbonate (EC/DMC/EMC, 1:1:1 vol%) as the electrolyte. The cells were tested at current density of 60  $\text{mA g}^{-1}$  between 4.2 V and 1.3 V with a Neware battery testing system.

## 3. Results and discussion

Fig. 1 shows the XRD patterns of  $\text{FeF}_2$  with a ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}] = 10:4.17$  synthesized for 1 h under 500, 550 and 650 °C. It showed that the diffraction peaks corresponding to  $\text{FeF}_2$  observed as a main phase in the sample synthesized at 500, 550 and 650 °C, although weak impurities corresponding to  $\text{Fe}_2\text{O}_3$  and  $\text{Fe}_3\text{O}_4$ . However, the peak intensity of  $\text{FeF}_2$  was decreased with the increase in the calcination temperature. In addition, XRD patterns of the nanocomposites did not show C peaks, suggesting that the C sheets are amorphous. This can be attributed to the decomposition temperature of PTFE, in which a drastic weight loss leading to the decomposition of PTFE was confirmed over 400 °C and PTFE is completely decomposed at 600 °C [10].

The electrochemical performance of the  $\text{FeF}_2$ /carbon composite as cathode was evaluated at room temperature. Fig. 2 shows the initial charge and discharge curves of the  $\text{FeF}_2$  in the 4.2–1.3 V region at a current density of 60  $\text{mA g}^{-1}$ . The

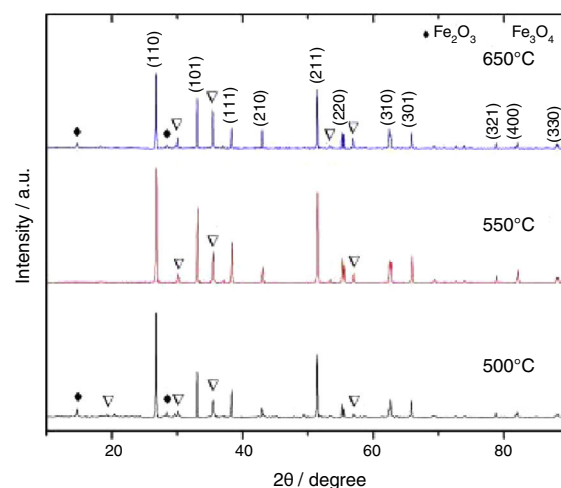


Fig. 1 – XRD patterns of  $\text{FeF}_2$  with a ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}] = 10:4.17$  synthesized for 1 h under 500, 550, and 650 °C.

initial discharge capacity of the  $\text{FeF}_2$  at 500, 550 and 650 °C can reach 212.67, 503.394 and 333.327  $\text{mA h g}^{-1}$ , respectively. The reversible capacity of the  $\text{FeF}_2$  obtained in this study was lower than that of the theoretical specific capacity (571  $\text{mA h g}^{-1}$ ). These results may be due to the  $\text{Fe}_2\text{O}_3$  and  $\text{Fe}_3\text{O}_4$  impurity phases observed in the sample, which would decrease the discharge capacity. However, the reversible capacity of the obtained  $\text{FeF}_2$  was higher than that of the  $\text{FeF}_2$ -carbon composite reported by Zhang et al. (345  $\text{mA h g}^{-1}$ ) [2]. The high discharge capacity is attributed to incorporation of carbon that might facilitate charge transfer at the interface. These results indicate that the optimum temperature is 550 °C.

Fig. 3 shows the XRD patterns of the sample synthesized at 550 °C for 1 h with function of different weight ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}]$ . It is obvious that the optimum weight ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}]$  for synthesis of  $\text{FeF}_2$  as a single phase is 10:4.17. There is a weak impurity corresponding to  $\text{Fe}_3\text{O}_4$  with


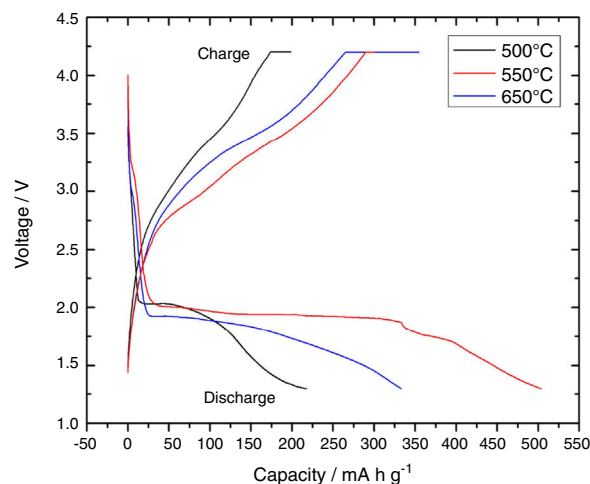


Fig. 2 – Initial charge and discharge curves of  $\text{FeF}_2$  with a weight ratio of  $[\text{FeC}_2\text{O}_4]:[\text{PTFE}] = 10:4.17$  synthesized at 500, 550, and 650 °C for 1 h in the 4.2–1.3 V region at a current density of 60  $\text{mA g}^{-1}$ .

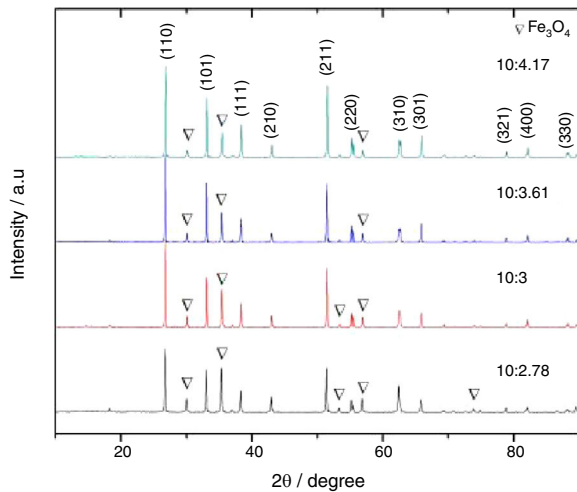


**Fig. 3 – XRD patterns of FeF<sub>2</sub> synthesized at 550 °C for 1 h with function of different weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE].**


different weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE]. The peak intensity of FeF<sub>2</sub> was increased and the impurity phase was decreased with the increase of PTFE. It is indicate that the optimum conditions of synthesis of FeF<sub>2</sub> using PTFE as a fluorine source are flowing that; i) weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] is 10:4.17, ii) calcination temperature is 550 °C.

Fig. 4a shows a TEM image of the synthesized FeF<sub>2</sub>/carbon nanoparticle. The image clearly shows that the obtained FeF<sub>2</sub> sample has granular particle morphology and a particle size of 50–100 nm. The carbon layer coated on the FeF<sub>2</sub> shows thickness less than 20 nm, providing a good electrical conduction path. Fig. 4b shows the clearly observable lattice fringes of the carbon layer, which correspond to an inter-planar (*d*) spacing of 0.5 nm. This result suggests that the particle growth of FeF<sub>2</sub> was effectively suppressed by using PTFE as the fluorine source due to the low decomposition temperature and high activation rate, which led to the short reaction time and low reaction temperature for synthesis of the FeF<sub>2</sub> sample.

Fig. 5a shows the initial charge and discharge curves of the FeF<sub>2</sub> in the 4.2–1.3 V region. The initial discharge capacity of the FeF<sub>2</sub> with a weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] = 10:2.78, 10:3, 10:3.61, 10:4.17 can reach 136.032, 168.098, 303.835 and 503.394 mA h g<sup>-1</sup>, respectively. It is due to the Fe<sub>3</sub>O<sub>4</sub> impurity phase observed in the sample, which would decrease the discharge capacity. These results indicate that the optimum weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] is 10:4.17. Fig. 5b shows the charge–discharge curves as a weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] = 10:4.17 at a current density of 60 mA g<sup>-1</sup>. During the first cycle, the composite delivers a discharge capacity of 503.394 mA h g<sup>-1</sup>, the reversible specific charge capacity is 300.427 mA h g<sup>-1</sup>. The reversible capacity of charge and discharge also decreased with increasing cycle number. The

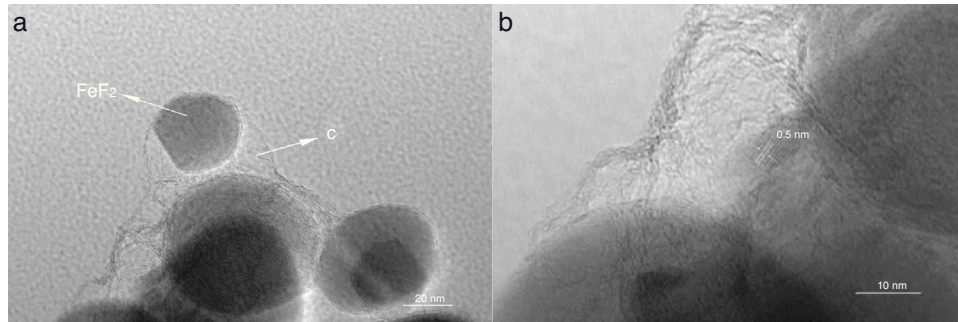

**Fig. 4 – TEM image of FeF<sub>2</sub>/carbon nanoparticle as with a weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] = 10:4.17 synthesized at 550 °C for 1 h.**

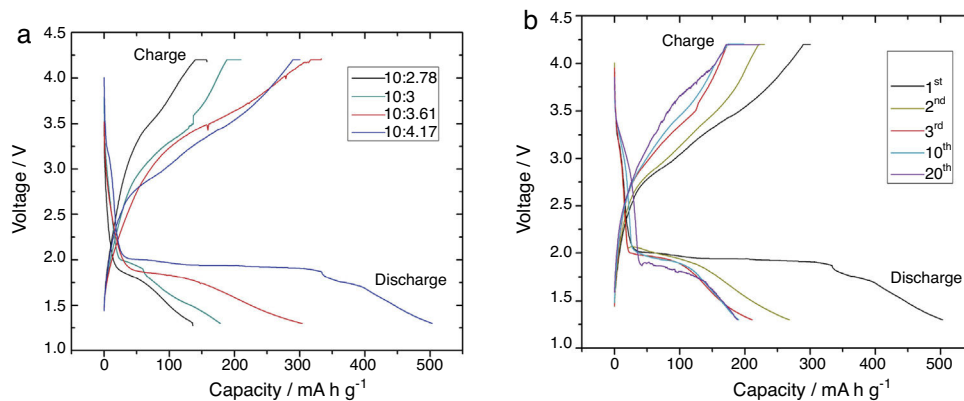

**Fig. 5 – Initial charge and discharge curves of FeF<sub>2</sub> synthesized at 550 °C for 1 h with function of different weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] in the 4.2–1.3 V region at a current density of 60 mA g<sup>-1</sup> (a), and charge–discharge curves with a weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] = 10:4.17 at a current density of 60 mA g<sup>-1</sup> (b).**

discharge capacities are found to be 268.478, 211.34, 193.817 and 183.328 mA h g<sup>-1</sup> at the 2nd, 3rd, 10th, and 20th cycles, respectively. In addition, the voltage plateau was confirmed in the 2.0 V in the discharge curves. This region involves the conversion reaction, accompanied by the formation of Fe and LiF. In the following cycles, the plateaus are almost the same, which may be attributed to the improvement on conductivity due to generation of iron nanoparticles in the conversion reaction. The voltage plateau is lower than the theoretical voltage (2.66 V). The possible reasons are as follows. The thick carbon layer presents a longer diffusion length, thus limiting Li<sup>+</sup> diffusion and hindering electrolyte penetration. So, decreasing the thickness of carbon layer and the particle size of FeF<sub>2</sub> will be explored in further investigation.

#### 4. Conclusions

In summary, FeF<sub>2</sub>/carbon composite nanoparticle was synthesized successfully by a one-pot thermal reaction using polytetrafluoroethylene (PTFE) as a fluorine source. It is indicated that the optimum conditions of synthesis of a single phase FeF<sub>2</sub> are flowing that: a) calcination temperature is 550 °C; b) weight ratio of [FeC<sub>2</sub>O<sub>4</sub>]:[PTFE] is 10:4.17. The composite exhibits an initial discharge capacity of 503.394 mA h g<sup>-1</sup> at a current density of 60 mA g<sup>-1</sup> in voltage range of 4.2–1.3 V. The specific discharge capacities to be 268.478, 211.34, 193.817 and 183.328 mA h g<sup>-1</sup> at the 2nd, 3rd, 10th, and 20th cycles, respectively.

#### Conflicts of interest

The authors declare no conflicts of interest.

#### Acknowledgements

The authors gratefully acknowledge the Joint Funds of the National Natural Science Foundation of China (Grant No. U1202272).

#### REFERENCES

- [1] Dunn B, Kamath H, Tarascon JM. Electrical energy storage for the grid: a battery of choices. *Science* 2011;334:928–35.
- [2] Zhang YL, Wang L, Li JJ, Wen L, He XM. A one-pot approach towards FeF<sub>2</sub>-carbon core-shell composite and its application in lithium ion batteries. *J Alloys Compounds* 2014;606:226–30.
- [3] Chu QX, Xing ZC, Tian JQ, Ren XB, Asiri AM, Al-Youbi AO, et al. Facile preparation of porous FeF<sub>3</sub> nanospheres as cathode materials for rechargeable lithium-ion batteries. *J Power Sources* 2013;236:188–91.
- [4] Badway F, Pereira N, Cosandey F, Amatucci GG. Carbon-metal fluoride nanocomposites structure and electrochemistry of FeF<sub>3</sub>:C. *J Electrochem Soc* 2003;150:1209–18.
- [5] Badway F, Cosandey F, Pereira N, Amatucci GG. Carbon metal fluoride nanocomposites high-capacity reversible metal fluoride conversion materials as rechargeable positive electrodes for Li batteries. *J Electrochem Soc* 2003;150:1318–27.
- [6] Plitz I, Badway F, Al-Sharab J, DuPasquier A, Cosandey F, Amatucci GG. Structure and electrochemistry of carbon-metal fluoride nanocomposites fabricated by solid-state redox conversion reaction. *J Electrochem Soc* 2005;152:307–15.
- [7] Wang F, Robert R, Chernova NA, Pereira N, Omenya F, Badway F, et al. Conversion reaction mechanisms in lithium ion batteries: study of the binary metal fluoride electrodes. *J Am Chem Soc* 2011;133:18828–36.
- [8] Li C, Gu L, Tsukimoto S, Aken PA, Maier J. Low-temperature ionic-liquid-based synthesis of nanostructured iron-based fluoride cathodes for lithium batteries. *Adv Mater* 2010;22:3650–4.
- [9] Li C, Gu L, Tong J, Tsukimoto S, Maier J. A mesoporous iron-based fluoride cathode of tunnel structure for rechargeable lithium batteries. *Adv Funct Mater* 2011;21:1391–7.
- [10] Torii H, Uematsu K, Toda K, Sato M. Synthesis of FeF<sub>3</sub> fluoride electrode material using polytetrafluoroethylene. *J Ceram Soc Jpn* 2014;122:473–6.